


Article number: O.E Test number: 10 Mean Count: Nec 32
 1/2 LOT:426 (FIKSAJLI) 32/1 TR
 Tests: 2/ 500 v = 400 m/min. FV = 9.23 cN

TestCounter: 7.1M
 TesterNo: 4716-xxxx

USTER QUALITY REPORT

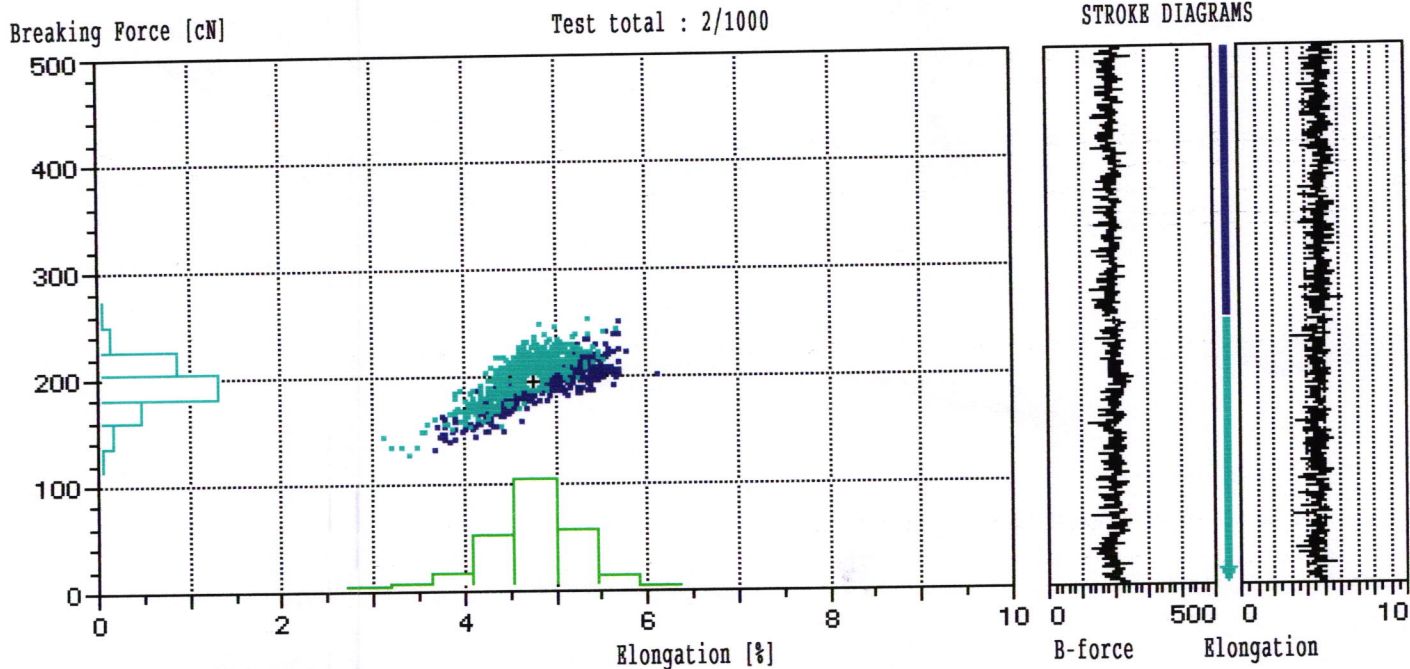

Color key: Tests 1 2

B-force	Elongation	Tenacity	B-work
[cN]	[%]	[cN/tex]	[cN.cm]

Overall results: (total)

2 Tests /	1000 Single tests			
Mean values	195.9	4.75	10.61	264.4
CV%	10.07	8.83	10.07	16.43
s +/-	19.7	0.42	1.07	43.4
Q95% +/-	1.2	0.03	0.07	2.7
Max values	252.0	6.10	13.65	393.3
Min values	125.2	3.11	6.79	131.0
P0.01: (0)				
P0.05: (0)				
P0.1 : (1)	125.2	3.11	6.79	131.0
P0.5 : (5)	134.0	3.47	7.26	142.5
P1.0 : (10)	142.8	3.67	7.74	155.9

Weak points (0cN,) F = 0

Stil O.E Örnek ID 02064 Nom. numara Nec 32 Nom. büküm
Testler 2 / 1 v= 400 m/min t= 1 min Ölçüm yarigi 4 Kısa elyaf

Tablo

Artikel RIETER Materyal sinifi İplik Maki. Nr. 10-TR
IG:1/2 LOT:426 (FIKSAJLI)

Toplam testler : 2 / 2 Tek test(ler)

Nr	U%	CVm	CVm 3m	CVm 10m	DR 1.5m 5%	İnce -40%	İnce -50%	Kalin +35%	Kalin +50%	Neps +200%	Neps +280%	Rel. Num. ±
	%	%	%	%	%	/km	/km	/km	/km	/km	/km	%
1	12.99	16.36	3.51	2.70	23.4	1060	105.0	1135	125.0	892.5	42.5	0.4
2	12.92	16.27	3.65	2.83	20.4	985	97.5	1038	117.5	790.0	40.0	-0.4
Ortalama	12.96	16.32	3.58	2.77	21.9	1023	101.3	1086	121.3	841.3	41.3	0.0
CV												
Q95												
Max	12.99	16.36	3.65	2.83	23.4	1060	105.0	1135	125.0	892.5	42.5	0.4
Min	12.92	16.27	3.51	2.70	20.4	985	97.5	1038	117.5	790.0	40.0	-0.4