


Article number: 0.E Test number: 1 Mean Count: Nec 30
 1/2 LOT:423 (FIKSAJLI) 30/1 TR
 Tests: 2/ 500 v = 400 m/min. FV = 9.84 cN

TestCounter: 5.5M
 TesterNo: 4716-xxxx

USTER QUALITY REPORT

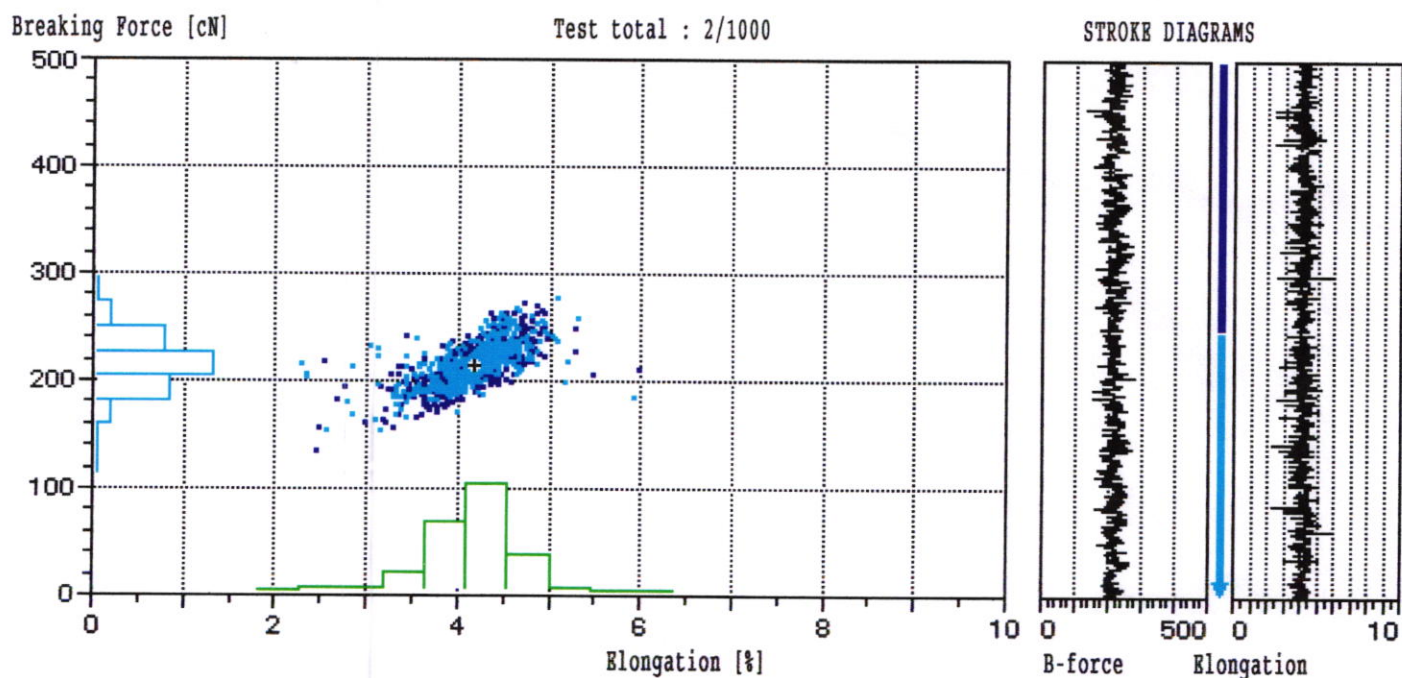

Color key: Tests 1 2

B-force	Elongation	Tenacity	B-work
[cN]	[%]	[cN/tex]	[cN.cm]

Overall results: (total)

	2 Tests /	1000 Single tests		
Mean values	215.3	4.16	10.94	258.8
CV%	9.56	10.41	9.56	17.74
s +/-	20.6	0.43	1.05	45.9
Q95% +/-	1.3	0.03	0.06	2.8
Max values	275.4	5.96	13.99	409.6
Min values	134.0	2.27	6.81	90.8
P0.01:(0)				
P0.05:(0)				
P0.1 :(1)	134.0	2.27	6.81	90.8
P0.5 :(5)	155.3	2.46	7.89	125.2
P1.0 :(10)	163.3	2.79	8.30	139.9

Weak points (0cN,) F = 0

Stil O.E Örnek ID 01081 Nom. numara Nec 30 Nom. büküm
Testler 2 / 1 v= 400 m/min t= 1 min Ölçüm yarigi 4 Kısa elyaf

Tablo

Artikel RIETER Materyal sinifi İplik Maki. Nr. 1-TR
IG:1/2 LOT:423 (FIKSAJLI)

Toplam testler : 2 / 2 Tek test(ler)

Nr	U%	CVm	CVm 3m	CVm 10m	DR 1.5m 5% %	İnce -40% /km	İnce -50% /km	Kalin +35% /km	Kalin +50% /km	Neps +200% /km	Neps +280% /km	Rel. Num. ± %
1	12.88	16.23	3.02	2.21	19.5	1008	87.5	1153	152.5	680.0	27.5	-0.4
2	12.87	16.21	3.86	3.00	27.8	1100	107.5	1115	125.0	685.0	25.0	0.4
Ortalama	12.88	16.22	3.44	2.60	23.6	1054	97.5	1134	138.8	682.5	26.3	0.0
CV Q95												
Max	12.88	16.23	3.86	3.00	27.8	1100	107.5	1153	152.5	685.0	27.5	0.4
Min	12.87	16.21	3.02	2.21	19.5	1008	87.5	1115	125.0	680.0	25.0	-0.4