
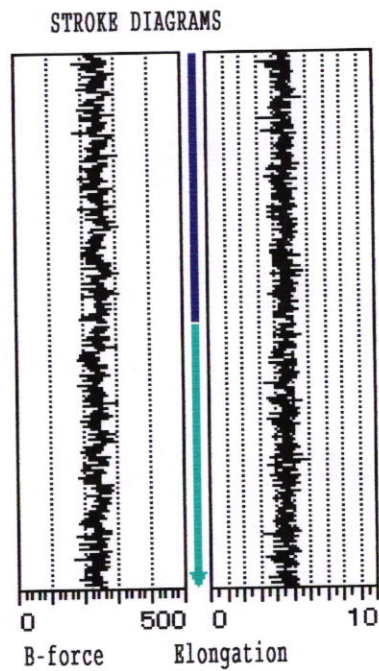


Article number: OE Test number: 2 Mean Count: Nec 30
 1/2 LOT:423 (FIKSAJLI) 30/1 DK
 Tests: 2/ 500 v = 400 m/min. FV = 9.84 cN

TestCounter: 6.9M
 TesterNo: 4716-xxxx

USTER QUALITY REPORT

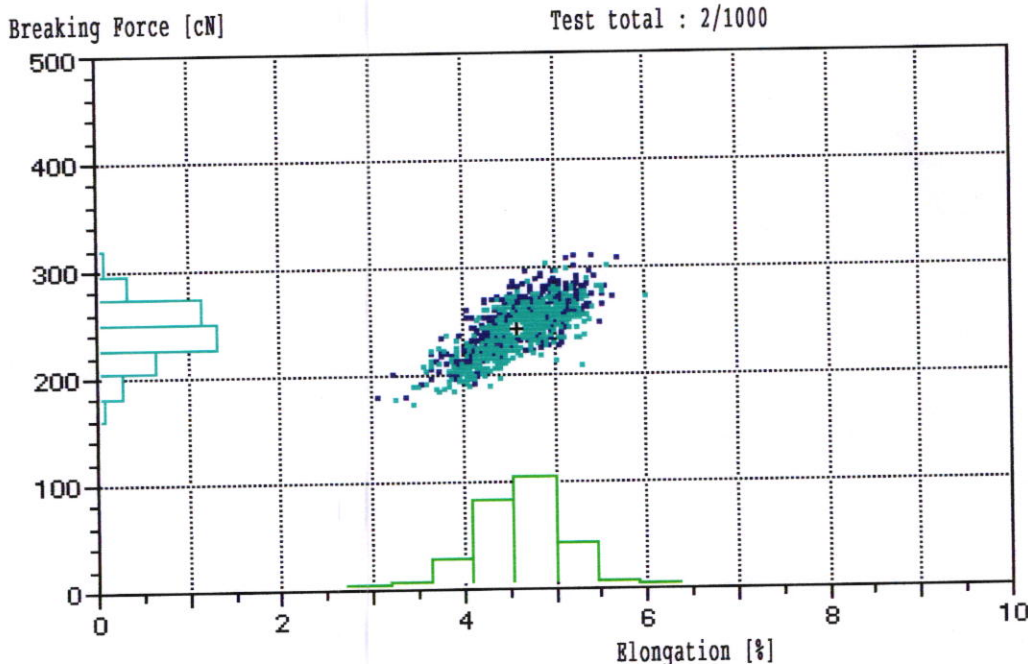

Color key: Tests 1 2

B-force	Elongation	Tenacity	B-work
[cN]	[%]	[cN/tex]	[cN.cm]

Overall results: (total)

2 Tests / 1000 Single tests				
Mean values	243.5	4.60	12.37	309.6
CV%	9.56	8.78	9.56	16.75
s +/-	23.3	0.40	1.18	51.9
Q95% +/-	1.4	0.03	0.07	3.2
Max values	310.5	5.98	15.78	483.2
Min values	172.1	3.05	8.74	156.3
P0.01: (0)				
P0.05: (0)				
P0.1 : (1)	172.1	3.05	8.74	156.3
P0.5 : (5)	183.1	3.44	9.30	178.1
P1.0 : (10)	187.5	3.58	9.53	185.6

Weak points (0cN,) F = 0

Stil O.E Örnek ID 01951 Nom. numara Nec 30 Nom. büküm
Testler 2 / 1 v= 400 m/min t= 1 min Ölçüm yarigi 4 Kısa elyaf

Tablo

Artikel RIETER Materyal sinifi İplik Maki. Nr. 2-DK
IG:1/2 LOT:423 (FIKSAJLI)

Toplam testler : 2 / 2 Tek test(ler)

Nr	U%	CVm	CVm 3m	CVm 10m	DR 1.5m 5% %	İnce -40% /km	İnce -50% /km	Kalin +35% /km	Kalin +50% /km	Neps +200% /km	Neps +280% /km	Rel Num. ± %
1	12.86	16.25	3.66	2.69	25.8	902.5	80.0	1158	172.5	652.5	27.5	-0.5
2	12.50	15.76	2.86	2.00	15.6	877.5	82.5	1030	147.5	550.0	32.5	0.5
Ortalama CV Q95	12.68	16.01	3.26	2.35	20.7	890.0	81.3	1094	160.0	601.3	30.0	0.0
Max	12.86	16.25	3.66	2.69	25.8	902.5	82.5	1158	172.5	652.5	32.5	0.5
Min	12.50	15.76	2.86	2.00	15.6	877.5	80.0	1030	147.5	550.0	27.5	-0.5