


Article number: OE Test number: 7 Mean Count: Nec 30
 1/2 LOT:425 (FIKSAJLI) 30/1 TR
 Tests: 2/ 500 v = 400 m/min. FV = 9.84 cN

TestCounter: 6.8M
 TesterNo: 4716-xxxx

USTER QUALITY REPORT

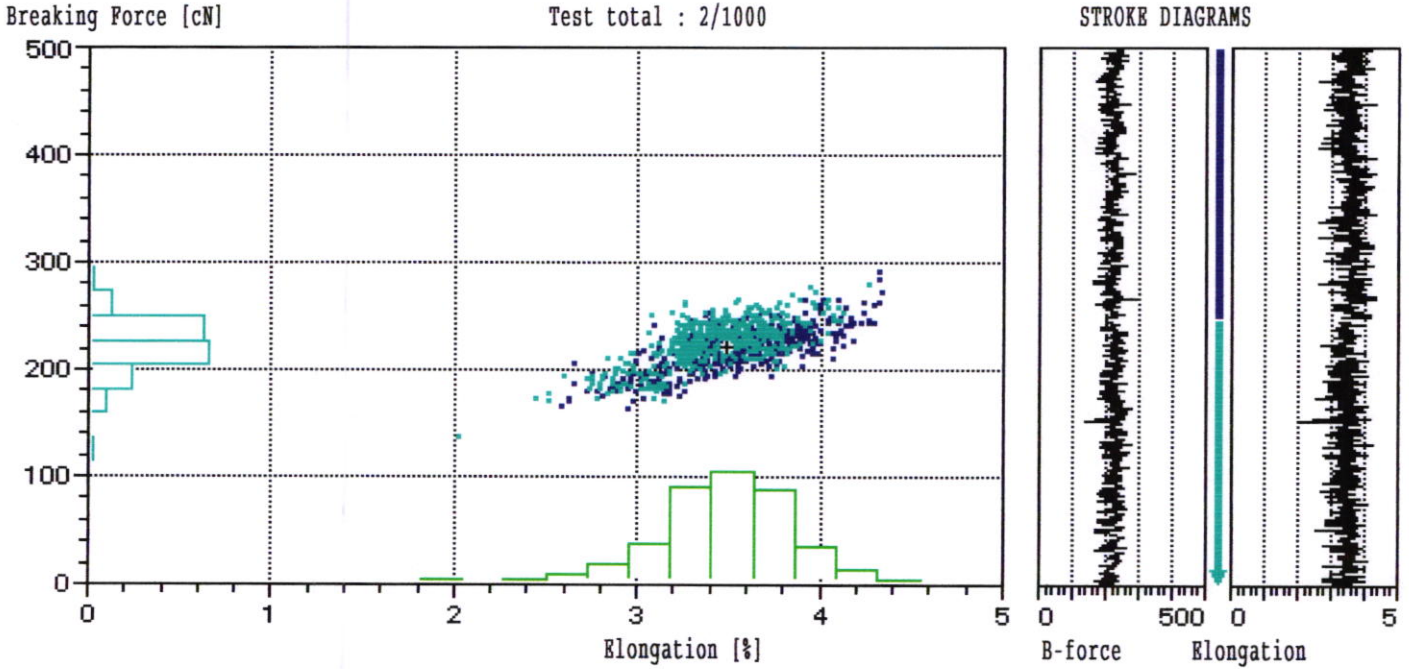

Color key: Tests 1 2

	B-force [cN]	Elongation [%]	Tenacity [cN/tex]	B-work [cN.cm]
Overall results: (total)				
2 Tests / 1000 Single tests				
Mean values	222.3	3.49	11.30	215.4
CV%	9.02	9.14	9.02	16.38
s +/-	20.1	0.32	1.02	35.3
Q95% +/-	1.2	0.02	0.06	2.2
Max values	289.3	4.33	14.70	331.3
Min values	134.8	2.01	6.85	79.2
P0.01:(0)				
P0.05:(0)				
P0.1 :(1)	134.8	2.01	6.85	79.2
P0.5 :(5)	169.2	2.58	8.60	114.8
P1.0 :(10)	171.4	2.65	8.71	133.2

Weak points (0cN,) F = 0

Stil O.E Örnek ID 01869 Nom. numara Nec 30 Nom. büküm
Testler 2 / 1 v= 400 m/min t= 1 min Ölçüm yarigi 4 Kısa elyaf

Tablo

Artikel RIETER Materyal sinifi Iplik Maki. Nr. 7-TR
IG:1/2 LOT:425 (FIKSAJLI)

Toplam testler : 2 / 2 Tek test(ler)

Nr	U%	CVm	CVm 3m	CVm 10m	DR 1.5m 5% %	İnce -40% /km	İnce -50% /km	Kalin +35% /km	Kalin +50% /km	Neps +200% /km	Neps +280% /km	Rel. Num ± %
1	11.87	14.94	3.70	2.99	18.9	532.5	15.0	725.0	75.0	360.0	22.5	0.3
2	11.85	14.95	3.24	2.37	16.8	625.0	40.0	757.5	70.0	332.5	17.5	-0.3
Ortalama	11.86	14.94	3.47	2.68	17.8	578.8	27.5	741.3	72.5	346.3	20.0	0.0
CV												
Q95												
Max	11.87	14.95	3.70	2.99	18.9	625.0	40.0	757.5	75.0	360.0	22.5	0.3
Min	11.85	14.94	3.24	2.37	16.8	532.5	15.0	725.0	70.0	332.5	17.5	-0.3