


Article number: 0.E Test number: 1 Mean Count: Nec 26
 1/2/3 LOT:426 (FIKSAJLI) 26/1 TR
 Tests: 3/ 500 v = 400 m/min. FV = 11.36 cN

TestCounter: 7.2M
 TesterNo: 4716-xxxx

USTER QUALITY REPORT

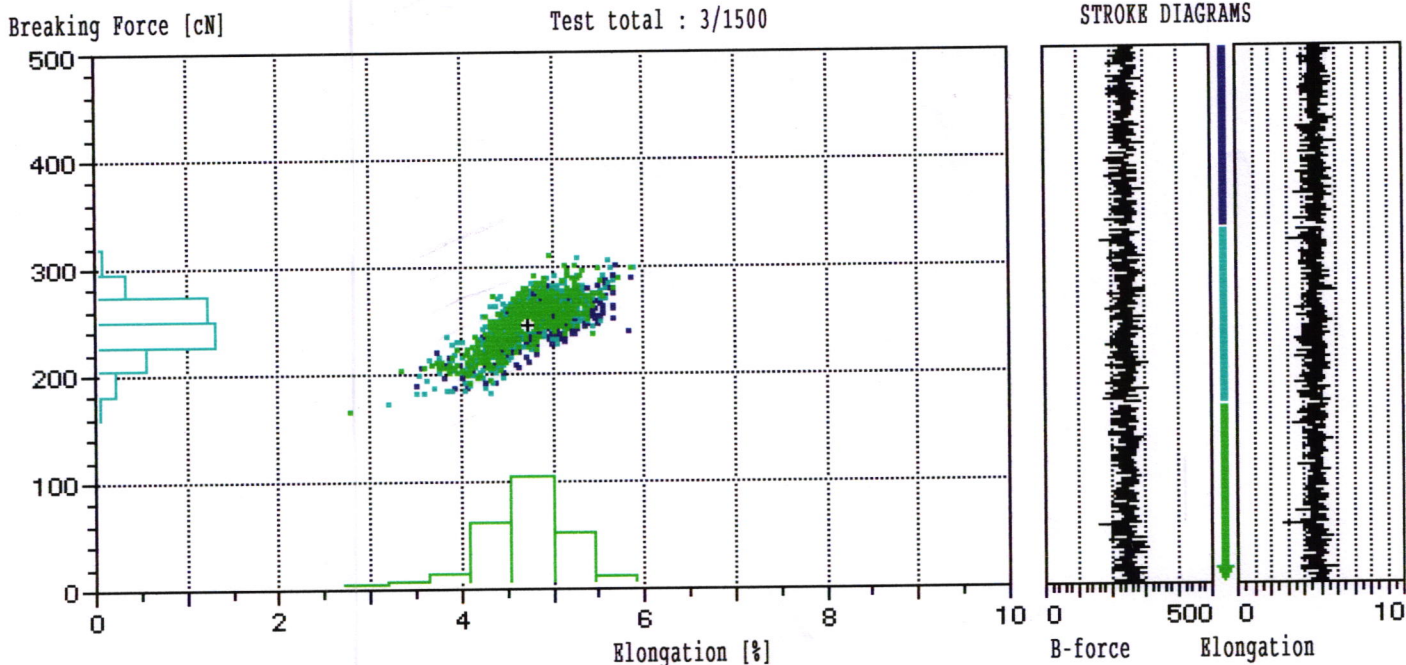

Color key: Tests 1 2 3

B-force	Elongation	Tenacity	B-work
[cN]	[%]	[cN/tex]	[cN.cm]

Overall results: (total)

	3 Tests /	1500 Single tests		
Mean values	244.9	4.73	10.78	324.7
CV%	8.96	8.28	8.96	15.62
s +/-	21.9	0.39	0.97	50.7
Q95% +/-	1.1	0.02	0.05	2.6
Max values	309.1	5.88	13.61	506.5
Min values	164.1	2.76	7.22	115.6
PO.01:(0)				
PO.05:(0)				
PO.1 :(1)	164.1	2.76	7.22	115.6
PO.5 :(7)	182.4	3.57	8.03	193.4
P1.0 :(15)	188.2	3.73	8.29	208.2

Weak points (0cN,) F = 0

Stil O.E Örnek ID 02121 Nom. numara Nec 26 Nom. büküm
Testler 3 / 1 v= 400 m/min t= 1 min Ölçüm yarığı 3 Kısa elyaf

Tablo

Artikel RIETER Materyal sinifi İplik Maki. Nr. 1-TR
IG:1/2/3 LOT:426 (FIKSAJLI)

Toplam testler : 3 / 3 Tek test(ler)

Nr	U%	CVm	CVm 3m	CVm 10m	DR 1.5m 5% %	İnce -40% /km	İnce -50% /km	Kalin +35% /km	Kalin +50% /km	Neps +200% /km	Neps +280% /km	Rel Num ± %
1	10.90	13.70	2.91	1.82	12.7	327.5	10.0	407.5	30.0	72.5	7.5	1.5
2	11.20	14.10	3.48	2.59	16.1	370.0	40.0	525.0	52.5	132.5	10.0	-1.3
3	11.10	14.00	3.30	2.11	16.8	412.5	32.5	495.0	45.0	112.5	2.5	-0.2
Ortalama	11.06	13.93	3.23	2.17	15.2	370.0	27.5	475.8	42.5	105.8	6.7	0.0
CV												
Q95												
Max	11.20	14.10	3.48	2.59	16.8	412.5	40.0	525.0	52.5	132.5	10.0	1.5
Min	10.90	13.70	2.91	1.82	12.7	327.5	10.0	407.5	30.0	72.5	2.5	-1.3