


Article number: 0.E Test number: 3 Mean Count: Nec 30
 1/2/3/4/5 LOT:225 (FIKSAJLI) 30/1 DK
 Tests: 5/ 500 v = 400 m/min. FV = 9.84 cN

TestCounter: 7.3M
 TesterNo: 4716-xxxx

USTER QUALITY REPORT

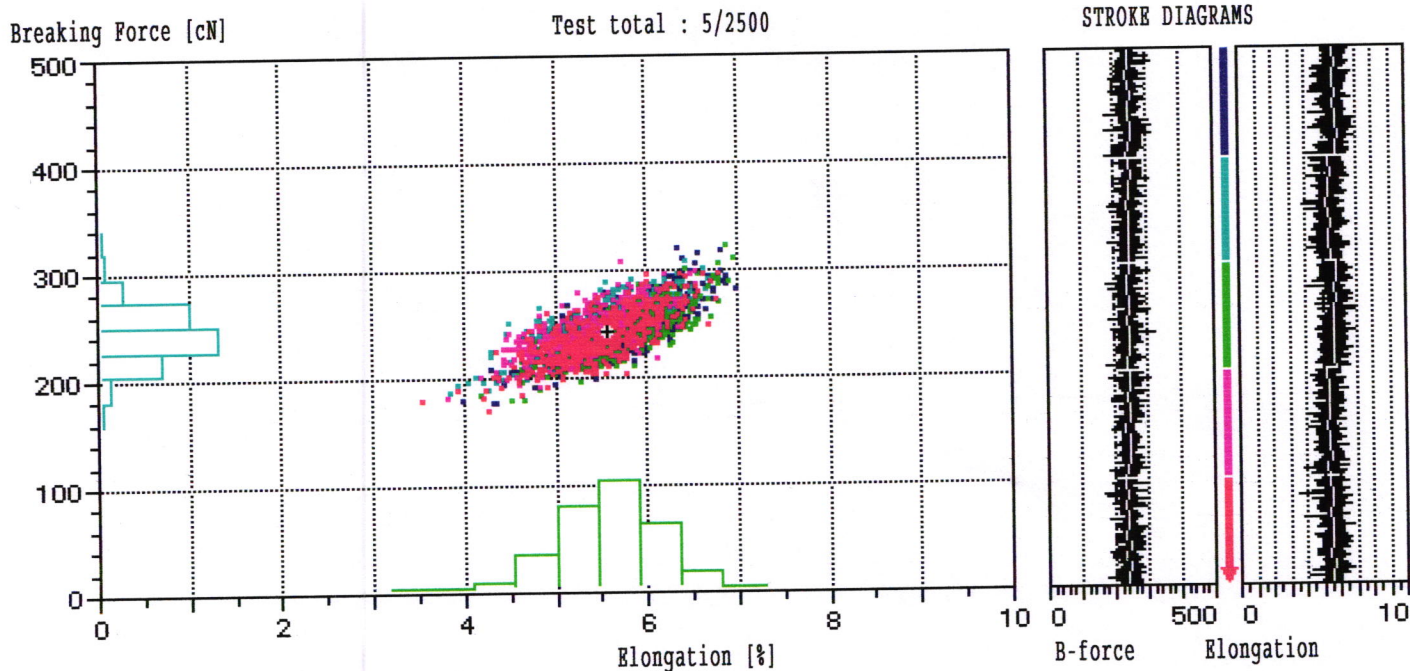

Color key: Tests 1 2 3 4 5

B-force	Elongation	Tenacity	B-work
[cN]	[%]	[cN/tex]	[cN.cm]

Overall results: (total)

5 Tests /	2500	Single tests		
Mean values	243.4	5.57	12.37	372.6
CV%	8.72	9.03	8.72	15.87
s +/-	21.2	0.50	1.08	59.1
Q95% +/-	0.8	0.02	0.04	2.3
Max values	320.8	6.97	16.30	573.2
Min values	169.9	3.54	8.63	174.1
P0.01:(0)				
P0.05:(1)	169.9	3.54	8.63	174.1
P0.1 :(2)	175.8	3.82	8.93	175.2
P0.5 :(12)	186.0	4.20	9.45	218.5
P1.0 :(25)	193.4	4.34	9.82	236.9

Weak points (0cN,) F = 0

Overall results: (between)

CV%	1.66	3.31	1.66	3.12
s +/-	4.0	0.18	0.20	11.6

Stil O.E Örnek ID 02201 Nom. numara Nec 30 Nom. bukümü
Testler 5 / 1 v= 400 m/min t= 1 min Ölçüm yarigi 4 Kısa elyaf

Tablo

Artikel SCHLAFHORST Materyal sinifi İplik Maki. Nr. 3-DK
İG:1/2/3/4/5 LOT:225 (FIKSAJLI)

Toplam testler : 5 / 5 Tek test(ler)

Nr	U%	CVm	CVm 3m	CVm 10m	DR 1.5m 5%	İnce -40%	İnce -50%	Kalin +35%	Kalin +50%	Neps +200%	Neps +280%	Rel Num %
	%	%	%	%	%	/km	/km	/km	/km	/km	/km	%
1	11.94	15.12	3.29	2.32	17.8	622.5	45.0	802.5	67.5	492.5	62.5	-0.6
2	11.97	15.17	3.32	2.73	22.7	612.5	32.5	825.0	105.0	680.0	60.0	0.4
3	11.51	14.54	2.79	2.11	14.8	495.0	30.0	567.5	65.0	412.5	27.5	-0.6
4	12.14	15.34	3.07	2.03	17.0	720.0	47.5	830.0	102.5	607.5	70.0	1.9
5	12.33	15.59	3.09	2.16	20.2	762.5	40.0	867.5	85.0	672.5	62.5	2.8
Ortalama	11.98	15.15	3.11	2.27	18.5	642.5	39.0	778.5	85.0	573.0	56.5	0.0
CV	2.6	2.6	6.8	12.3	16.43	16.2	19.5	15.4	22.1	20.4	29.5	1.8
Q95	0.38	0.48	0.26	0.35	3.8	129.4	9.5	149.3	23.3	145.3	20.7	2.2
Max	12.33	15.59	3.32	2.73	22.7	762.5	47.5	867.5	105.0	680.0	70.0	2.8
Min	11.51	14.54	2.79	2.03	14.8	495.0	30.0	567.5	65.0	412.5	27.5	-1.9